




Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the [Creative Commons Attribution License](#) which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

How to Cite:

Romero-Vázquez, P. B.; López-Moreno, S.; Errandonea, D. Stability of FeVO₄ II under Pressure: A First-Principles Study. *Crystals* 2022, 12, 1835. <https://doi.org/10.3390/cryst12121835>

Stability of FeVO₄-II under Pressure: A First-Principles Study

Pricila Betbirai Romero-Vázquez ¹, Sinhué López-Moreno ^{2,3,*} and Daniel Errandonea ⁴

¹ División de Materiales Avanzados, IPICYT, Camino a la presa de San José 2055 Col. Lomas 4a sección, San Luis Potosí 78126, Mexico

² CONACYT—División de Materiales Avanzados, IPICYT, Camino a la presa de San José 2055 Col. Lomas 4a sección, San Luis Potosí 78126, Mexico

³ Centro Nacional de Supercomputo, IPICYT, Camino a la presa de San José 2055 Col. Lomas 4a sección, San Luis Potosí 78126, Mexico

⁴ Departamento de Física Aplicada, Instituto de Ciencias de Materiales, MALTA Consolider Team, Universidad de Valencia, 46100 Valencia, Spain

* Correspondence: sinhue.lopez@ipicyt.edu.mx

Abstract: In this work, we report first-principles calculations to study FeVO₄ in the CrVO₄-type (phase II) structure under pressure. Total-energy calculations were performed in order to analyze the structural parameters, the electronic, elastic, mechanical, and vibrational properties of FeVO₄-II up to 9.6 GPa for the first time. We found a good agreement in the structural parameters with the experimental results available in the literature. The electronic structure analysis was complemented with results obtained from the Laplacian of the charge density at the bond critical points within the Quantum Theory of Atoms in Molecules methodology. Our findings from the elastic, mechanic, and vibrational properties were correlated to determine the elastic and dynamic stability of FeVO₄-II under pressure. Calculations suggest that beyond the maximum pressure covered by our study, this phase could undergo a phase transition to a wolframite-type structure, such as in CrVO₄ and InVO₄.

Keywords: FeVO₄ under pressure; CrVO₄-type structure; first-principles; mechanical properties; vibrational properties; electronic properties



Citation: Romero-Vázquez, P. B.; López-Moreno, S.; Errandonea, D. Stability of FeVO₄-II under Pressure: A First-Principles Study. *Crystals* **2022**, *12*, 1835. <https://doi.org/10.3390/cryst12121835>

Academic Editor: Artem R. Oganov

Received: 18 November 2022

Accepted: 13 December 2022

Published: 15 December 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

High-pressure studies on ABO₄ compounds have increased in the last two decades due to the evolution of the diamond-anvil cell (DAC) and its impact on other relevant areas, such as materials sciences [1,2]. Among ABO₄ compounds, those with a CrVO₄-type structure (Space Group, SG, *Cmcm*, No. 63, *Z* = 4, with [6 – 4] coordination for the [A-B cations]) have received less attention. CrVO₄-type compounds are a family formed mainly by phosphates, vanadates, chromates, and sulfates [3]. Given their position in the Bastide diagram [4], it has been reported that they could have a structural phase transition driven by pressure to the wolframite [5,6] or zircon [7,8] structure. This implies a change in the coordination to [6 – 4 + 2] and [8 – 4] in the high-pressure phases, respectively.

According to the literature, AVO₄ vanadates with CrVO₄-type structures have been used in applications as photocatalyst materials [1,9,10], cathodoluminescent materials [11,12], and scintillators [13,14], among others. The properties of these compounds are reported to be highly dependent on the occupation of the *d* valence electrons of the transition metal cations [9–14]. Until now, only four vanadates with a CrVO₄-type structure have been reported: CrVO₄ [6], FeVO₄ [15], InVO₄ [16], and the less studied TiVO₄ [3]. Unlike the other vanadates, FeVO₄ presents a great polymorphism, crystallizing at ambient conditions in the triclinic AlVO₄-type [17] structure (SG: *P* $\bar{1}$, No. 2, *Z* = 6) [15], while the CrVO₄-type phase was obtained from high-pressure-high-temperature studies [18] and synthesized at ambient conditions by hydrothermal method [19]. Further, the antiferromagnetic order in FeVO₄-II was observed after the characterization of its magnetic properties [19]. However, until now, no more experimental or theoretical studies have been reported to characterize this phase. It

is worth mentioning that most of the studies carried out at high pressure on this compound have focused on characterizing the crystal structure of the different polymorphs [15,18,20–22].

In this work, we performed a first-principles characterization of FeVO₄-II up to 9.6 GPa. The main goal is to determine the elastic and dynamic stability of the studied polymorph at ambient conditions and under pressure. In this sense, a complete report of the elastic constants, mechanical properties, elastic anisotropy, and vibrational properties is presented. Furthermore, given the relevance of the electronic structure of this compound in materials science, we computed the density of states and the band structure together with an analysis of the charge density with the QTAIM methodology [23,24].

2. Computational Details

Total energy calculations were performed within the framework of the density functional theory (DFT) [25] and the projector-augmented wave (PAW) [26,27] method as implemented in the Vienna *Ab initio* Simulation Package (VASP) [28–31]. We used a plane-wave energy cutoff of 520 eV to ensure high precision in our calculations. The exchange–correlation energy was described within the generalized gradient approximation (GGA) in the Perdew–Burke–Ernzerhof for solids (PBEsol) formulation [32]. The GGA+*U* was used to account for the strong correlation between the electrons in the *d* shell, on the basis of Dudarev’s method [33]. In this method, the Coulomb interaction *U* and the onsite exchange interaction *J_H* are treated together as $U_{\text{eff}} = U - J_{\text{H}}$. For our GGA+*U* calculations, we choose *U* = 6 eV and *J_H* = 0.95 eV. Similar values were previously used with relative success in the study of other iron and vanadate compounds [15,20,34–37].

The Monkhorst-Pack scheme was employed for the Brillouin-zone (BZ) integrations [38] with a mesh $4 \times 3 \times 3$, which corresponds to a set of 8 special *k*-points in the irreducible BZ. In the relaxed equilibrium configuration, the forces are less than 0.3 meV/Å per atom in each Cartesian direction. The highly converged results on forces are required for the calculations of the dynamical matrix using the direct force constant approach [39], which allows us to identify the irreducible representation and the character of the phonon modes at the zone center (Γ point). The phonon density of states (PDOS) were obtained from the calculation of the phonons in the whole BZ with a supercell $2 \times 2 \times 2$ times the conventional unit cell by using the PHONON software. The calculations of elastic constants were made following the methodology validated in Ref. [40] with a *k*-points mesh of $8 \times 6 \times 6$, a plane-wave energy cutoff of 570 eV, and a POTIM parameter of 0.016. The elastic tensor is determined by performing six finite distortions of the lattice and deriving the elastic constants from the strain–stress relationship [41]. The electron density was computed with a refined grid to be analyzed within the fundamentals of Quantum Theory of Atoms in Molecules (QTAIM) [42] with CRITIC [43,44], and AIM [45] codes.

3. Results and Discussion

3.1. Crystal Structure

According to the literature, FeVO₄ has been successfully synthesized as a metastable polymorph at ambient conditions in the orthorhombic CrVO₄-type structure (SG: *Cmcm*, No. 63, *Z* = 4) [19], also called the FeVO₄-II phase, see Figure 1a. In this structure, there are four non-equivalent Wyckoff positions (WP): Fe occupies the 4*a* (0, 0, 0), V the 4*c* (0, *y*, 1/4), and O the 8*f* (0, *y*, *z*), and 8*g* (*x*, *y*, 1/4). Internally, the structure consists of edge-sharing FeO₆ distorted octahedra along the *c* direction. The –FeO₆–FeO₆– chains are linked together by means of the VO₄ distorted tetrahedra, while the VO₄ tetrahedra are not linked to each other, as can be seen in Figure 1b. As shown in Figure 1c, there are two non-equivalent interatomic distances in the FeO₆ octahedra, the apical Fe–O distance ($d_{\text{Fe–O1}}$) and the equatorial Fe–O distance ($d_{\text{Fe–O2}}$). In the VO₄ tetrahedra, there are two V–O interatomic distances ($d_{\text{V–O1}}$ and $d_{\text{V–O2}}$). In both polyhedra, the respective interatomic distance $d_{\text{X–O2}}$ is larger than $d_{\text{X–O1}}$ (*X* = Fe, V). Inside the polyhedrons, there are important angles to mention that are relevant for the structural changes in the polyhedra under pressure. The α

angle is formed between the equatorial plane of the FeO_6 octahedra and the polar bond, while the β (γ) angle is between the two d_1 (d_2) interatomic distances of the VO_4 tetrahedra.

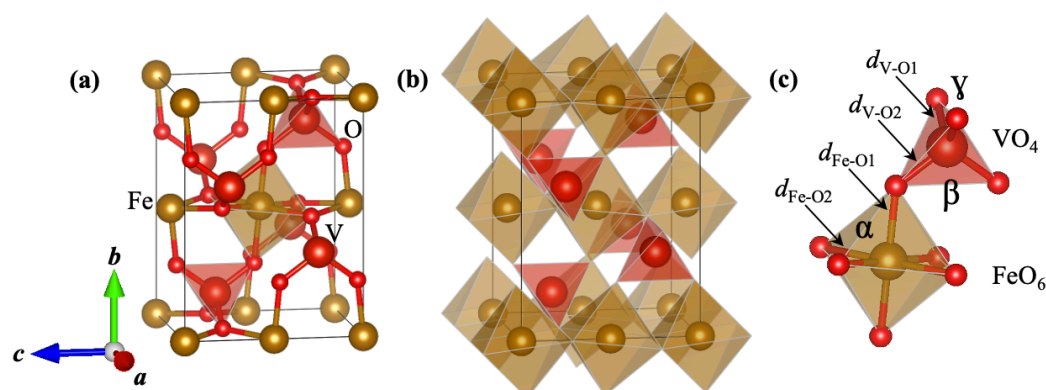


Figure 1. (a) Crystal structure of $\text{FeVO}_4\text{-II}$ polymorph, (b) polyhedral representation of the structure, and (c) irregular polyhedra of FeO_6 and VO_4 units. The different bond distances mentioned in the text are labeled as well as the bond angles. We used the VESTA software [46] to build the structures.

The equilibrium volume and unit-cell parameters at $P \approx 0$ GPa were computed by minimizing the total crystal energy for different volumes ranging from -4 to 10 GPa while allowing the internal atomic positions and the lattice parameters to relax. We used the third-order Birch–Murnaghan [47] equation-of-state (EOS) to fit the volume–energy curve. Our results showed that the lowest energy configuration is obtained when an antiferromagnetic coupling between Fe ions is obtained, in accordance with the experimental results from Mössbauer effect [19]. The optimized lattice parameters (a , b , c), volume (V), interatomic distances ($d_{\text{Fe-O}1}$, $d_{\text{Fe-O}2}$, $d_{\text{V-O}1}$, $d_{\text{V-O}2}$), internal angles (α , β , γ), bulk modulus (B) and pressure derivative of B (B') appear in Table 1 together with experimental results from the literature [19]. Furthermore, we have included the reported parameters for other CrVO_4 -type structure vanadates for comparison. According to Table 1, the equilibrium volume at ambient pressure of AVO_4 ($A = \text{Cr, Fe, In, Tl}$) compounds increases with the atomic mass of cation A , while the opposite occurs for bulk modulus. The obtained results for $\text{FeVO}_4\text{-II}$ are in excellent agreement with experiments, with a difference of less than 1% in the lattice parameters. For this volume, the WPs are $4a$ (0, 0, 0) for Fe, $4c$ (0, 0.35788, 1/4) for V, $8f$ (0, 0.76239, 0.96753), and $8g$ (0.26481, 0.47778, 1/4) for O. Following Table 1, the equilibrium volume at ambient pressure of AVO_4 ($A = \text{Cr, Fe, In, Tl}$) compounds increases with the atomic mass of cation A . In contrast, the opposite occurs for bulk modulus.

Table 1. Calculated structural parameters for $\text{FeVO}_4\text{-II}$ phase. a , b , and c are the lattice parameters, V is the volume, $d_{X-\text{O}n}$ ($X = \text{Fe, V}; n = 1, 2$) and α , β , and γ , are the interatomic distances and angles inside the crystal structure, respectively (see Figure 1). B is the bulk modulus and B' is the pressure derivative of B . Results from this work are denoted with \star . We also include experimental results from the literature of AVO_4 compounds for comparison.

	a (Å)	b (Å)	c (Å)	V (Å ³)	$d_{\text{Fe-O}1}$ (Å)	$d_{\text{Fe-O}2}$ (Å)	$d_{\text{V-O}1}$ (Å)	$d_{\text{V-O}2}$ (Å)	α (°)	β (°)	γ (°)	B (GPa)	B'	Ref.
FeVO_4	5.6038	8.2624	6.1726	285.80	1.9734	2.0377	1.6705	1.7842	89.271	106.990	112.547	88.8	2.8	\star
	5.5941	8.3216	6.2252	289.80	1.9784	2.0521	1.6544	1.7762				88.3	3.2	DFT [15]
	5.6284	8.2724	6.1118	284.57	2.0060	2.0290	1.6520	1.7920	89.600	107.200	112.500			Exp. [19]
CrVO_4	5.5785	8.2830	6.0576	279.90								93.0	4.0	DFT [6]
	5.5680	8.2080	5.9770	273.16								63.0	4.0	Exp. [6]
InVO_4	5.7547	8.6168	6.6751	331.00	2.1877	2.1392	1.6690	1.7824				71.0	4.0	DFT [5]
	5.7380	8.4920	6.5820	320.72								69.0	4.0	Exp. [16]
TlVO_4	5.8390	8.6870	6.8000	344.92										Exp. [48]

According to the most recent high-pressure experiments carried out on FeVO_4 [15,20], this compound undergoes the following phase transition sequence, $P\bar{1} \rightarrow P\bar{1}' \rightarrow \alpha\text{-MnMoO}_4$ -type, driven by pressure. However, previous high-pressure studies reported

the next phase transition sequence $P\bar{1} \rightarrow \text{CrVO}_4\text{-type} \rightarrow \text{wolframite}$ in a small range of pressure [49]. Therefore, it is unknown if the $\text{CrVO}_4\text{-type}$ structure of FeVO_4 would transition to wolframite when high-pressure experiments are carried out starting from the $\text{CrVO}_4\text{-type}$ structure, as occurs with CrVO_4 [6] and InVO_4 [5,16], and was predicted through first-principles calculations [15]. Therefore, from now on, we will only deal with studying the behavior of $\text{FeVO}_4\text{-II}$ under pressure without considering whether the $\text{CrVO}_4 \rightarrow \text{wolframite}$ transition occurs. Figure 2 shows the pressure evolution of the structural parameters for the $\text{FeVO}_4\text{-II}$ phase. According to Figure 2a, a volume reduction of $\Delta V = -9\%$ is observed for a range of pressure of ≈ 10 GPa. Considering the anisotropy of the orthorhombic crystal structure, ΔV is more reflected in the [010] and [001] directions, while the change in [100] is practically negligible, see Figure 2b. Indeed the compressibility of the [001] direction is comparable to the linear compressibility of diamond, making the studied material a near zero linear compressibility material along [001]. The anisotropy can also be understood with the help of the other internal parameters from Figure 2c–f. As seen in Figure 2c, the interatomic distances $d_{\text{Fe-O}n}$ of FeO_6 undergo more changes than the $d_{\text{V-O}n}$ distances of VO_4 , which is reflected in the larger compressibility of V_{FeO_6} octahedra against the minimal change in V_{VO_4} , see Figure 2d. Hence, the large compressibility of the y -axis is due primarily to the compressibility of octahedra due to the reduction in $d_{\text{Fe-O}2}$. Whereas, despite the reduction in $d_{\text{V-O}2}$, the β and γ angles adjust in such a way that V_{VO_4} remains almost constant with pressure. On the other hand, the distortion parameter Δ_d presents an important change at 6.2 GPa, which will be discussed in detail in Section 3.3.

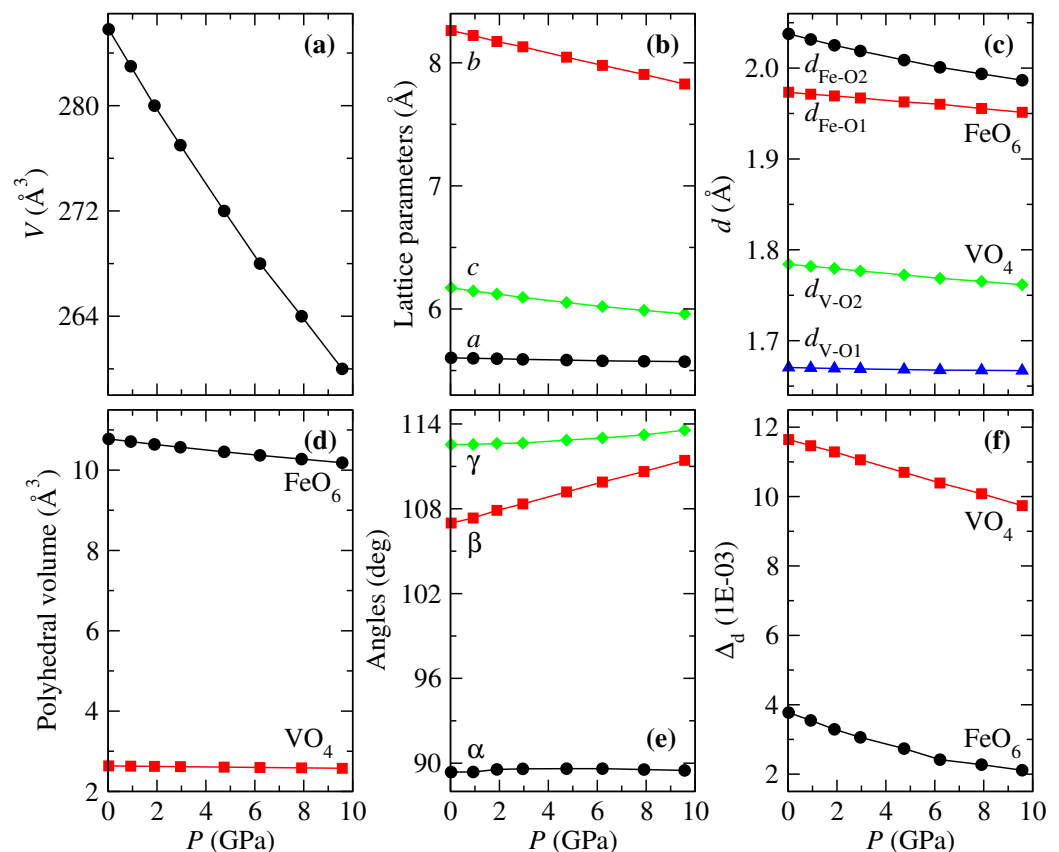


Figure 2. Structural parameters for $\text{FeVO}_4\text{-II}$ as a function of pressure: (a) volume, (b) lattice parameters, (c) interatomic distances, (d) polyhedral volumes, (e) angles, and (f) polyhedral distortion parameter.

3.2. Electronic Structure

Figure 3a,b displays our calculated density of states (DOS) and band structures along the high-symmetry path $Z-\Gamma-S-R-Z-T-Y-\Gamma$ of the $\text{FeVO}_4\text{-II}$ phase at ambient pressure and 9.6 GPa, respectively. Red dashed lines at 0 eV indicate the Fermi level. At ambient

pressure, the valence band maximum (VBM) is located at an H ($\frac{1}{2}, \frac{1}{2}, -u$) point (between T and Y), mainly occupied by $2p$ (p_x) states from oxygen. In contrast, the conduction band minima (CBM) is located at the Γ point with contributions of the $3d$ states from Fe, mostly from d_{yz} sub-orbital. Therefore, FeVO_4 -II phase presents an indirect energy band-gap $E_g = 2.11$ eV. In comparison, the direct Γ - Γ energy band-gap is 2.17 eV. In this case, the maximum at Γ below the Fermi level is occupied by $2p$ (p_x and p_y) states from oxygen, as happens in other ABO_4 compounds [40]. It has been reported that CBM of many rare-earth AVO_4 vanadates is dominated by vanadium $3d$ states, which makes these compounds present energy band-gaps close to 3.8 eV [50,51]. However, in the case of vanadates InVO_4 (phase II), CrVO_4 (phase II), and FeVO_4 (phase I), the energy band-gap lowers to 3.2, 2.6, and 2.1 eV, respectively, due to contribution from cation A to the valence and conduction band [5,6,50,52]. Hence, our E_g value follows the observed results for those vanadates. According to partial electronic DOS of Figure 3a, the states below the Fermi level mainly belong to the O atoms. In contrast, the states above the conduction bands are due to Fe, followed by V and O.

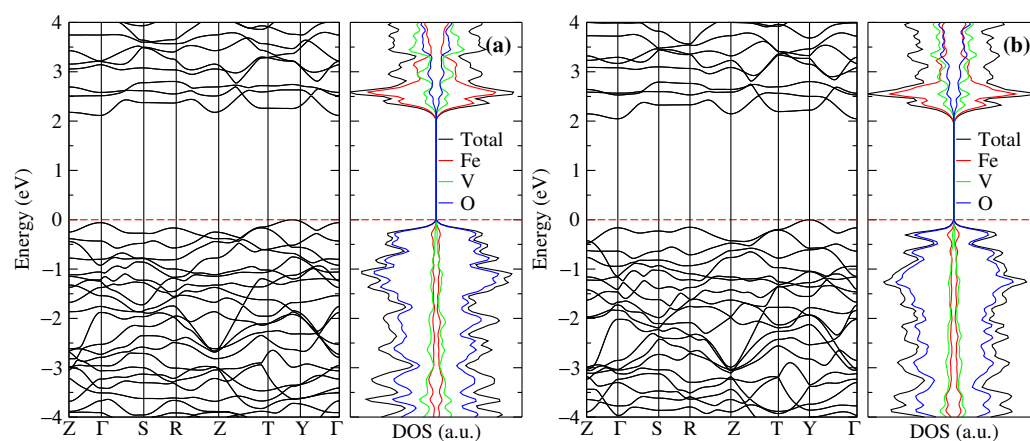


Figure 3. Band structure and electronic density of states at (a) ambient pressure and (b) 9.6 GPa of FeVO_4 -II phase.

As pressure increases up to 9.6 GPa, the VBM shifts to the high-symmetry point Y while the CBM is still at the Γ point with the same band occupation observed at ambient pressure, see Figure 3b. Hence, at this pressure, the band-gap is still indirect with $E_g = 2.05$ eV, which gives a pressure coefficient of $dE_g/dp = -7.1$ meV/GPa. In contrast, the pressure coefficients for InVO_4 and CrVO_4 are positive, with values of 13.5 [52] (8.9 [5]) meV for InVO_4 and 1.9 (4.1) meV for CrVO_4 [6], obtained by optical absorption measurements (DFT calculations). On the other hand, the forbidden direct Γ - Γ band-gap increases with pressure up to 2.21 eV at 9.6 GPa, which gives a value of $dE_g/dp = 4.2$ meV, similar to the obtained values for the other AVO_4 vanadates.

We performed a topological analysis of the charge density (ρ) with the QTAIM methodology to complement the study of the electronic structure of FeVO_4 -II. Figure 4a,b show the gradient vector field of the electron density ($\nabla\rho$) of FeO_6 and VO_4 polyhedra, respectively (gold for Fe, purple for V, and red for O). Blue points indicate the atomic nucleus, corresponding to the maximum critical points (MCP). The minimal CP (mCP) are in green, and the bond CPs (BCPs) are in black and are located in the bond path (blue dashed lines) between Fe (V) and O. The distance between Fe (V) and the BCP (d_{BCP}) is plotted as a function of pressure in Figure 4c. As seen, the distances d_{BCP} follow the same trend observed in the interatomic distances of Figure 2c. Therefore, the crystal structure can be interpreted in terms of charge density. In this sense, the Laplacian of the charge density ($\nabla^2\rho_{\text{BCP}}$) at the BCP gives an idea of the ionicity ($\nabla^2\rho_{\text{BCP}} > 0$) or covalency ($\nabla^2\rho_{\text{BCP}} < 0$) of a system [53]. According to Figure 4d, the Fe–O and V–O bonds have an ionic nature. The obtained values of $\nabla^2\rho_{\text{BCP}}$ (0.214–0.295 a.u.) for Fe–O bonds in the distorted octahedra are larger than those reported for A–O bonds in AWO_4 (0.086–0.147 a.u.) [54], AMoO_4 (0.085–0.22 a.u.) [53], and

ATcO_4 (0.045–0.153 a.u.) [40] compounds. In the case of the VO_4 distorted tetrahedra, there is a significant difference in the values of $\nabla^2\rho_{\text{BCP}_1}$ and $\nabla^2\rho_{\text{BCP}_2}$, which is related to the interatomic distances $d_{\text{V-O}_n}$ (see Table 1) being significantly larger than those obtained for the FeO_6 distorted octahedra. This is the reason for the low compressibility of the VO_4 polyhedra. As the pressure grows, the Laplacian values increase, strengthening the Fe–O and V–O bonds and the resistance of the polyhedrons to compression.

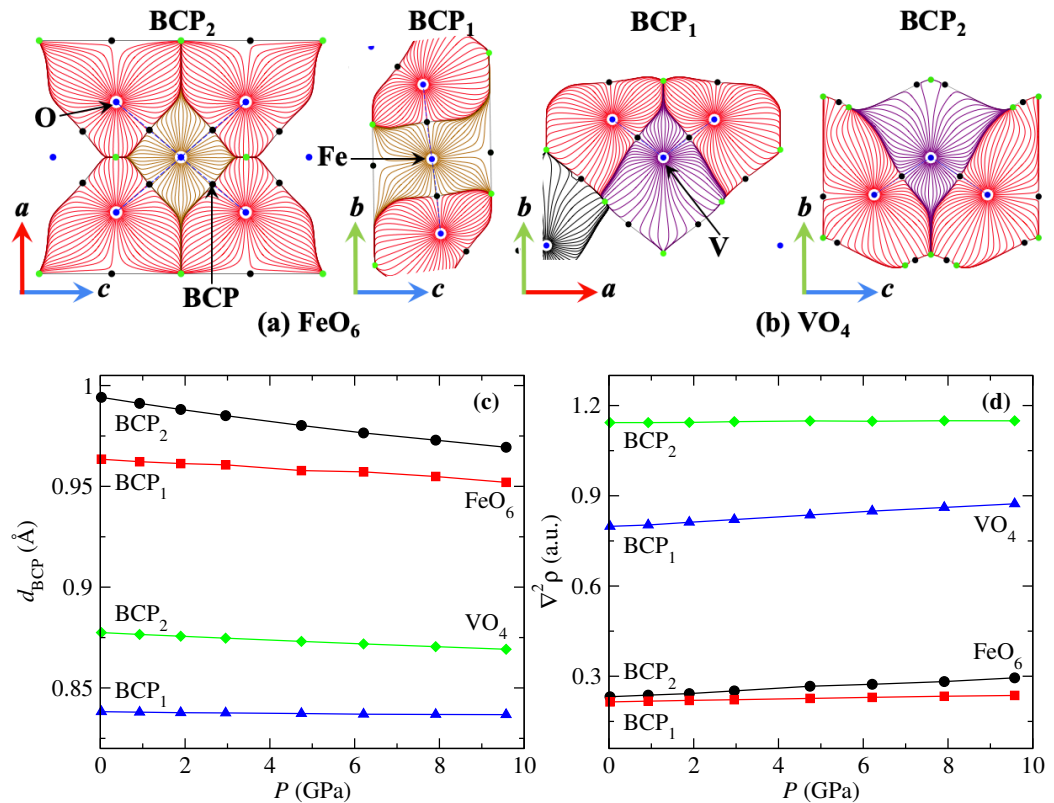


Figure 4. Gradient vector field of the electron density ($\nabla\rho$) for (a) FeO_6 and (b) VO_4 polyhedra. (c) Evolution of the interatomic distances from the cations to the critical bond points and (d) Laplacian of the charge density at the critical bond point as a function of pressure for FeVO_4 .

3.3. Elastic constants and mechanical properties

The elastic constants (c_{ij}) determine the resistance to deformation in the directions and planes of a crystal, making them highly dependent on the system's symmetry. For the orthorhombic crystalline system, there are nine independent elastic constants: c_{11} , c_{22} and c_{33} for longitudinal compression, c_{12} , c_{13} and c_{23} for transverse expansion, c_{44} , c_{55} , and c_{66} for pure shear [55]. Table 2 shows the elastic constants c_{ij} of $\text{FeVO}_4\text{-II}$ at 0 GPa and the respective pressure coefficients dc_{ij}/dP . The necessary and sufficient Born stability criteria for orthorhombic systems are [56]: $c_{11} > 0$, $c_{11}c_{22} > c_{12}^2$, $c_{11}c_{22}c_{33} + 2c_{12}c_{13}c_{33} + 2c_{12}c_{13}c_{23} - c_{11}c_{23}^2 - c_{22}c_{13}^2 - c_{33}c_{12}^2 > 0$, $c_{44} > 0$, $c_{55} > 0$, and $c_{66} > 0$, which are fulfilled for $\text{FeVO}_4\text{-II}$. Under hydrostatic pressure (P), the stability criteria are [57]: $c_{ii} - P > 0$ ($i = 1$ to 6), $c_{11} + c_{22} + c_{33} + 2c_{12} + 2c_{13} + 2c_{23} + 3P > 0$, $c_{11} + c_{22} - 2c_{12} - 4P > 0$, $c_{11} + c_{33} - 2c_{13} - 4P > 0$, and $c_{22} + c_{33} - 2c_{23} - 4P > 0$, which are also met. According to Table 2, the elastic constant c_{11} presents the higher value, followed by c_{33} and c_{22} , indicating that longitudinally the crystal is more resistant to deformation in the a -axis; this was also observed in the evolution of the lattice parameters under pressure in Figure 2b. As would be expected, the largest transverse expansion constant is c_{12} , followed by c_{13} and c_{23} , c_{33} being the smallest of the nine elastic constants. At the same time, the shear elastic constants are generally small against those from longitudinal compression and transverse expansion. We found that elastic constants follow a linear trend with pressure, where only c_{22} presents

a negative pressure coefficient related to the trends observed in the structural parameters with pressure.

Table 2. Elastic constants c_{ij} (in GPa) at 0 GPa and pressure coefficients.

	c_{11}	c_{22}	c_{33}	c_{44}	c_{55}	c_{66}	c_{12}	c_{13}	c_{23}
c_{ij}	234.2	125.5	144.8	62.98	52.49	47.04	78.46	68.21	39.81
dc_{ij}/dP	2.41	−0.87	3.78	0.74	1.04	0.15	2.39	2.18	2.57

The elastic constants and compliances were used to compute the bulk (B) and shear (G) modulus with the Hill procedure [58], which is the average of the Voigt (V) [59] and Reuss (R) [60] methods. The bulk modulus in the Voigt and Reuss methods is computed as follows: $9B_V = (c_{11} + c_{22} + c_{33} + 2c_{12} + 2c_{13} + 2c_{23})$, and $B_R^{-1} = (s_{11} + s_{22} + s_{33} + 2s_{12} + 2s_{13} + 2s_{23})$, respectively. While the shear modulus is obtained with the following equations: $15G_V = (c_{11} + c_{22} + c_{33} - c_{12} - c_{23} - c_{13} + 3c_{44} + 3c_{55} + 3c_{66})$, and $15G_R^{-1} = [4(s_{11} + s_{22} + s_{33}) - 4(s_{12} + s_{13} + s_{23}) + 3(s_{44} + s_{55} + s_{66})]$, respectively. B and G in the Hill average are obtained by means of $B = (B_V + B_R)/2$ and $G = (G_V + G_R)/2$, respectively. On the other hand, Young's modulus (E) and Poisson's ratio (ν) are given by $E = 9BG/(3B + G)$ and $\nu = (3B - 2G)/(6B + 2G)$, respectively. The Vickers hardness was calculated with the approximation of Tian et al. [61]: $H_v = 0.92 k^{1.137} G^{0.708}$, $k = G/B$.

The mechanical properties and their evolution with pressure are provided in Figure 5. As seen, B increases almost linearly with pressure, which means that the resistance to deformation increases for this pressure range. Whereas G undergoes a change in the linear trend above 3 GPa, reaching a maximum value of 53.9 at 6.2 GPa and falling down to 53.3 GPa at 9.6 GPa. There is no significant change in G for this pressure range, but the change in trend will substantially affect the other properties that depend on G . Interestingly, in other materials, such change in the slope of the pressure dependence of the shear modulus G has been identified as a precursor effect of a phase transition observed at higher pressures [62]. According to the equations of Voigt and Reuss for G , the behavior of G is due to the negative pressure coefficient for c_{22} and the significant values of dc_{ij}/dP for the transverse expansion elastic constants. On the other hand, B behaves linearly because B_V (B_G) only sums the longitudinal and transverse elastic constants (compliances), while c_{22} (s_{22}) decreases with pressure, so the value of c_{22} affects B by a small constant factor.

The behavior of Young's modulus is similar to G due to its relation with this mechanical property. According to Figure 5c, E increases by 4.3 % in a pressure range of 7.86 GPa; above this pressure, it decreases from 138.1 to 137.6 GPa. This behavior indicates that FeVO_4 could undergo a phase transition from a CrVO_4 -type phase to another one at a relatively small pressure since it has been observed that FeVO_4 undergoes several phase transitions below 10 GPa, see Refs. [15,20] and references therein. The Poisson's ratio follows an increasing trend, taking values between 0.26 and 0.29, which are in the range for ceramic semiconductors (0.25–0.42) [63] and are similar for other ABO_4 compounds [40,54,64]. These values indicate that ionic contribution dominates in FeVO_4 -II. The Pugh relation, Figure 5e, represents the ductility or brittleness of the system. A value below 1.75 [11] reveals a tendency to brittleness, while a value greater than this indicates that the material behaves in a ductile manner. FeVO_4 -II presents a value of 1.745 at ambient pressure and increases to 2.06 at 9.6 GPa, which means that ductility increases with pressure. As was expected, FeVO_4 -II, as other ABO_4 compounds, presents a small Vickers hardness due to the relatively small values of B and G . Given the relation between H_V and B/G , it is natural that the Vickers hardness decreases with pressure, Figure 5f.

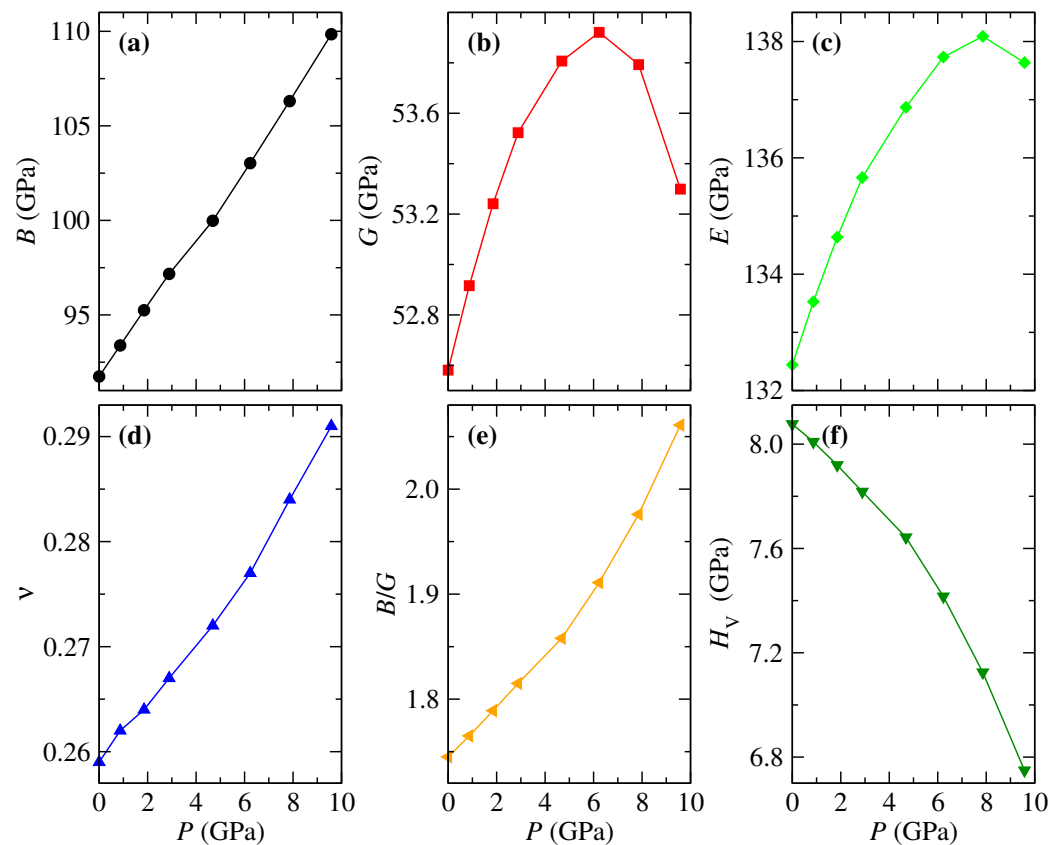


Figure 5. Pressure dependence of mechanical properties obtained from elastic constants with the Hill average: (a) bulk modulus, B , (b) shear modulus, G , (c) Young's modulus, E , (d) Poisson's ratio, ν , (e) Pugh's ratio, B/G , and (f) Vickers hardness, H_V , for $\text{FeVO}_4\text{-II}$.

On the other hand, elastic anisotropy has important implications in engineering science and crystal physics because it is commonly responsible for the formation of microcracks in materials [65]. In this work, we analyzed several anisotropic factors discussed below. The anisotropic shear factors provide a measure of the degree of anisotropy in the bonding between atoms in different crystallographic planes. The shear anisotropic factor for the {100} shear planes between the $\langle 011 \rangle$ and $\langle 010 \rangle$ directions is $A_{\{100\}} = 4c_{44}/(c_{11} + c_{33} - 2c_{13})$. For the {010} shear planes between $\langle 101 \rangle$ and $\langle 001 \rangle$ directions it is $A_{\{010\}} = 4c_{55}/(c_{22} + c_{33} - 2c_{23})$. For the {001} shear planes between $\langle 110 \rangle$ and $\langle 010 \rangle$ directions, it is $A_{\{001\}} = 4c_{66}/(c_{11} + c_{22} - 2c_{12})$. The factors $A_{\{100\}}$, $A_{\{010\}}$, and $A_{\{001\}}$ must be one for isotropic crystals, and any value greater or smaller than one measures the degree of elastic anisotropy. According to Figure 6a, $A_{\{100\}}$ presents the smallest deviation from one, followed by $A_{\{010\}}$ and $A_{\{001\}}$. However, once pressure is applied, $A_{\{010\}}$ is more affected than the others. Factor $A_{\{010\}}$ is related to the equatorial interatomic distances of the distorted octahedra [$d_{\text{Fe-O}2}$, see Figure 2c], which makes quite a bit of sense since it is $d_{\text{Fe-O}2}$ that undergoes the greatest change with pressure. While $A_{\{001\}}$ is more related to $d_{\text{Fe-O}1}$, with this interatomic distance being the second one most affected by pressure.

Other important factors are the universal anisotropy $A_U = 5G_V/G_R + B_V/B_R - 6$, the percentage of elastic anisotropy in bulk [$A_B = (B_V - B_R)/(B_V + B_R)$] and shear [$A_G = (G_V - G_R)/(G_V + G_R)$] modulus, where a value of zero is associated with isotropic elastic constants, which means that $B_V = B_R$ and $G_V = G_R$. For the entire range of pressure, A_B is larger than A_G because the difference between B_V and B_R is bigger than between G_V and G_R . However, the pressure affects more A_G than A_B as happens with G . This difference increases above 6.2 GPa as G_R presents the same behavior of G , while G_V is always increasing. A_U is larger than A_G and A_B since the anisotropies of both modules are added.

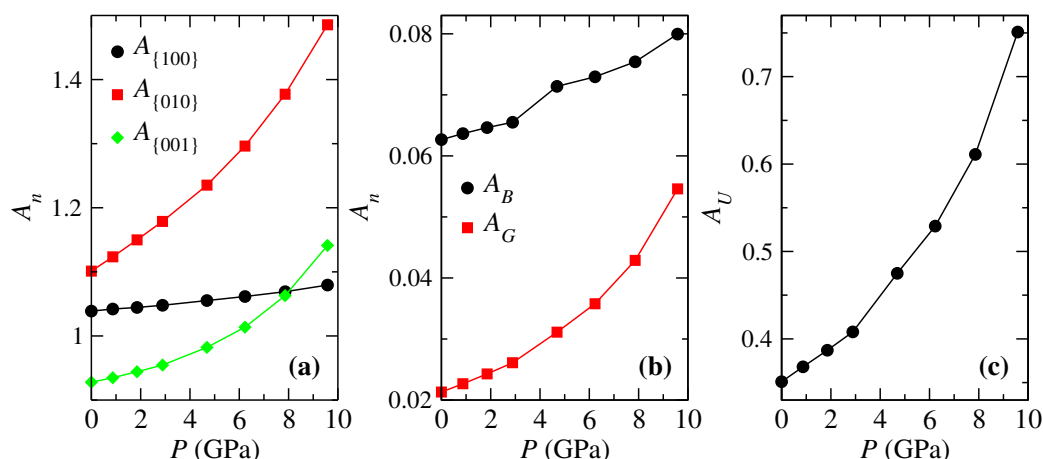


Figure 6. (a) Pressure dependence of anisotropy factors: (a) by crystallographic direction, (b) percentage bulk and shear anisotropy, and (c) universal anisotropy for FeVO₄-II.

3.4. Vibrational Properties

According to the group theory, the space group *Cmcm* has the following Raman, infrared (IR), and silent phonon modes at the zone center $\Gamma = 5A_g + 4B_{1g} + 2B_{2g} + 4B_{3g}$, $\Gamma = 6B_{1u} + 7B_{2u} + 5B_{3u}$, and $\Gamma = 3A_u$, respectively. These modes can be further classified into internal (symmetric stretching, ν_1 , symmetric bending, ν_2 , asymmetric stretching, ν_3 , and asymmetric bending, ν_4) and external (translational, T , and rotational, R) modes of VO₄ units. The calculated Raman, IR, and silent phonon frequencies, the pressure coefficients ($d\omega/dP$), and the Grüneisen parameters ($\gamma = -\partial \ln(\omega)/\partial \ln V$) at the Γ point appear in Table 3.

Table 3. Calculated Raman, infrared, and silent phonon frequencies (ω in cm⁻¹), pressure coefficients ($d\omega/dp$), and Grüneisen parameters (γ) of FeVO₄-II.

Mode	Raman			Mode	Infrared			Mode	Silent		
	ω	$d\omega/dp$	γ		ω	$d\omega/dp$	γ		ω	$d\omega/dp$	γ
$T(B_{3g})$	153.7	1.37	0.57	$T(B_{1u})$	153.7	0.24	0.15	$T(A_u)$	164.4	1.29	0.77
$T(B_{1g})$	177.4	-1.05	-0.82	$T(B_{1u})$	180.8	1.68	0.86	$\nu_2(A_u)$	220.3	0.55	0.23
$R(B_{1g})$	219.6	0.52	0.22	$R(B_{3u})$	201.2	-0.01	-0.03	$\nu_2(A_u)$	404.9	7.45	1.68
$T(A_g)$	221.8	3.23	1.29	$\nu_2(B_{2u})$	274.9	1.12	0.37				
$R(B_{2g})$	261.8	4.25	1.47	$\nu_4(B_{3u})$	298.8	1.51	0.46				
$\nu_2(A_g)$	355.1	0.30	0.07	$T(B_{3u})$	315.1	3.82	0.25				
$\nu_4(B_{3g})$	361.7	1.36	0.33	$\nu_4(B_{2u})$	327.9	-0.88	-1.06				
$\nu_2(B_{2g})$	366.4	3.78	0.94	$R(B_{1u})$	363.1	2.41	0.48				
$\nu_4(B_{1g})$	374.0	3.58	0.88	$\nu_4(B_{2u})$	381.5	6.61	1.61				
$\nu_4(A_g)$	394.2	1.55	0.36	$\nu_4(B_{1u})$	398.3	4.93	1.13				
$\nu_4(B_{3g})$	431.3	5.90	1.25	$\nu_2(B_{2u})$	420.6	4.38	0.92				
$\nu_3(B_{1g})$	652.8	5.71	0.78	$\nu_3(B_{3u})$	654.2	5.64	0.77				
$\nu_3(A_g)$	751.0	5.74	0.72	$\nu_3(B_{2u})$	735.8	5.47	0.67				
$\nu_1(A_g)$	918.9	1.33	0.12	$\nu_3(B_{1u})$	866.8	2.58	0.26				
$\nu_3(B_{3g})$	922.0	2.44	0.24	$\nu_3(B_{2u})$	924.3	1.38	0.13				

According to Table 3, one Raman, $R(B_{1g})$, and two IR modes, $R(B_{3u})$ and $\nu_4(B_{2u})$, have negative pressure coefficients and Grüneisen parameters (soften with pressure), which are related to the instability of the CrVO₄-type structure under pressure [2]. Such behavior was already observed in InVO₄ [5] and CrVO₄ [20]. The soft translational Raman $T(B_{1g})$ mode involves a translation of the VO₄ polyhedra accompanied by a rotation of the FeO₆ units around the z-axis as rigid units, see Figure 7, whose freedom of movement is affected by the decrease in the lattice parameter b , which is the most compressible under pressure. In contrast, the remaining Raman modes harden with pressure. The IR soft $R(B_{3u})$ mode is quite similar to the $R(B_{1g})$, but in this case, the FeO₆ vibrates asymmetrically. While the other soft B_{2u} mode implies the asymmetric bending in the VO₄ polyhedra with a translation of the Fe cation in the c direction, which produces a stretching of the apical $d_{\text{Fe-O1}}$ interatomic distances. Therefore, the softening of R and IR modes is related to the compression of the y -axis. Interestingly, phosphates with CrVO₄-type structure, such

as InPO_4 and TiPO_4 , only present some IR soft modes. The main difference being that Ti(In)PO_4 is more compressible in the $c(b)$ -axis [7].

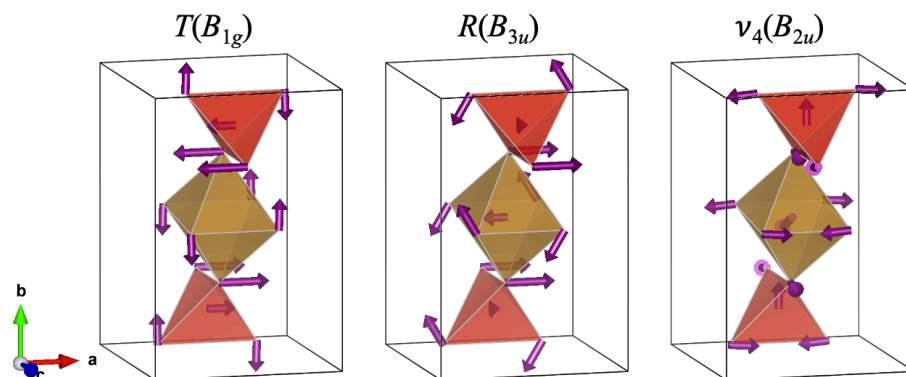


Figure 7. Eigenvectors of the phonon frequencies with negative pressure coefficients of $\text{FeVO}_4\text{-II}$. We used the VESTA software [46] to build the structures.

The phonon dispersion relation and the phonon density of states (DOS) are displayed in Figure 8 at (a) ambient pressure and (b) 9.6 GPa. As can be seen in Figure 8a, the CrVO_4 -type structure of FeVO_4 complains with the dynamic stability criteria at $P = 0$, which implies that $\omega^2(\mathbf{q}, s) > 0$ for all wave vectors \mathbf{q} and polarization s (longitudinal and transverse modes) [66]. Therefore, $\text{FeVO}_4\text{-II}$ complains with the elastic and dynamic stability criteria to be experimentally synthesized [19], such as InVO_4 [5] and CrVO_4 [20]. We can see no significant differences in the phonon spectrum at 9.6 GPa, which ensures that the $\text{FeVO}_4\text{-II}$ phase would be stable in a pressure range where the isostructural vanadates InVO_4 and CrVO_4 undergo a phase transition to the wolframite-type structure [5,20].

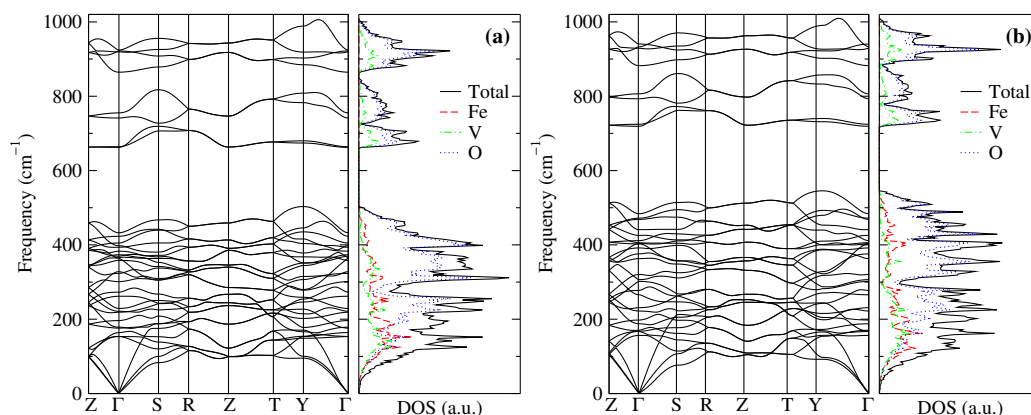


Figure 8. Phonon spectrum and phonon DOS at (a) 0 GPa, and (b) 9.6 GPa of $\text{FeVO}_4\text{-II}$.

The phonon DOS of $\text{FeVO}_4\text{-II}$ is more similar to CrVO_4 than InVO_4 because In is more than double the mass of Cr and Fe. The partial phonon DOS of the first lower frequency zone (up to $\approx 505 \text{ cm}^{-1}$) is due to external (R and T) and internal (ν_2 and ν_4) phonon modes, with Fe and V similar contributions. In contrast, the two high-frequency zones are due to pure internal vibrations ν_1 and ν_3 , which indicates that phonon DOS is only due to O and V.

4. Conclusions

First-principles calculations were performed to study FeVO_4 in the CrVO_4 -type structure up to 9.6 GPa. Our results indicate that this phase is elastically and dynamically stable for this pressure range. FeVO_4 presents an indirect band-gap $E_g = 2.11 \text{ eV}$, similar to the value reported for the triclinic phase of FeVO_4 at ambient pressure. The Laplacian charge density at BCPs in both polyhedra is larger than those reported for AMoO_4 and

AWO₄ compounds and increases with pressure. It was observed that the *y*-axis is the most compressible, related to the reduction in the interatomic distances of the FeO₆ polyhedra. These changes in the structural parameters have strong effects on the phonon modes with negative pressure coefficients. We found that the shear modulus *G* softens with pressure, which suggests that the FeVO₄-II phase could undergo a phase transition below 10 GPa as was predicted in a previous study and happen in CrVO₄ and InVO₄, where these compounds have a phase transition from CrVO₄-type to the wolframite structure. We hope this work encourages other research groups to perform high-pressure characterization studies with the diamond-anvil cell device in order to increase the knowledge of less studied orthovanadates with CrVO₄-type structure, such as FeVO₄ and TlVO₄.

Author Contributions: Methodology, P.B.R.-V., S.L.-M.; calculations, P.B.R.-V., S.L.-M.; writing—original draft preparation, P.B.R.-V., S.L.-M.; supervision, S.L.-M.; discussion, S.L.-M., D.E.; writing—review and editing, P.B.R.-V., S.L.-M., D.E. All authors have read and agreed to the published version of the manuscript.

Funding: S.L.-M. thanks CONACYT of Mexico for financial support through the program “Programa de Investigadoras e Investigadores por México”. D.E. thanks the financial support from the Spanish Ministerio de Ciencia e Investigación (10.13039/501100011033) under Project PID2019-106383GB-41, as well as through the MALTA Consolider Team research network (RED2018-102612-T) and from Generalitat Valenciana under Grants PROMETEO CIPROM/2021/075-GREENMAT and MFA/2022/007.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: All relevant data that support the findings of this study are available from the corresponding authors upon request.

Acknowledgments: The authors gratefully acknowledge the computing time granted by LANCAD and CONACYT on the supercomputer Miztli at LSVP DGTIC UNAM. Furthermore, the IPICYT Supercomputing National Center for Education and Research, grant TKII-R2022-SLM1/PBRV1.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Errandonea, D.; Manjon, F. Pressure effects on the structural and electronic properties of ABX₄ scintillating crystals. *Prog. Mater. Sci.* **2008**, *53*, 711–773. [[CrossRef](#)]
2. Errandonea, D.; Garg, A.B. Recent progress on the characterization of the high-pressure behaviour of AVO₄ orthovanadates. *Prog. Mater. Sci.* **2018**, *97*, 123–169. [[CrossRef](#)]
3. Baran, E. Materials belonging to the CrVO₄ structure type: Preparation, crystal chemistry and physicochemical properties. *J. Mater. Sci.* **1998**, *33*, 2479–2497. [[CrossRef](#)]
4. de Jesus Pereira, A.L.; Santamaría-Pérez, D.; Vilaplana, R.; Errandonea, D.; Popescu, C.; da Silva, E.L.; Sans, J.A.; Rodríguez-Carvajal, J.; Muñoz, A.; Rodríguez-Hernández, P.; et al. Experimental and Theoretical Study of SbPO₄ under Compression. *Inorg. Chem.* **2020**, *59*, 287–307. [[CrossRef](#)] [[PubMed](#)]
5. López-Moreno, S.; Rodríguez-Hernández, P.; Muñoz, A.; Errandonea, D. First-principles study of InVO₄ under pressure: phase transitions from CrVO₄-to AgMnO₄-type structure. *Inorg. Chem.* **2017**, *56*, 2697–2711. [[CrossRef](#)]
6. Botella, P.; López-Moreno, S.; Errandonea, D.; Manjón, F.J.; Sans, J.; Vie, D.; Vomiero, A. High-pressure characterization of multifunctional CrVO₄. *J. Phys. Condens. Matter.* **2020**, *32*, 385403. [[CrossRef](#)]
7. López-Moreno, S.; Errandonea, D. Ab initio prediction of pressure-induced structural phase transitions of CrVO₄-type orthophosphates. *Phys. Rev. B* **2012**, *86*, 104112. [[CrossRef](#)]
8. Dwivedi, A.; Kaiwart, R.; Varma, M.; Velaga, S.; Poswal, H. High-pressure structural investigations on InPO₄. *J. Solid State Chem.* **2020**, *282*, 121065. [[CrossRef](#)]
9. Butcher J., D.P.; Gewirth, A.A. Photoelectrochemical response of TlVO₄ and InVO₄: TlVO₄ composite. *Chem. Mater.* **2010**, *22*, 2555–2562. [[CrossRef](#)]
10. Zhao, C.; Tan, G.; Yang, W.; Xu, .; Liu, T.; Su, Y.; Ren, H.; Xia, A. Fast interfacial charge transfer in α -Fe₂O₃- δ C δ /FeVO₄- x + δ C x - δ bulk heterojunctions with controllable phase content. *Sci. Rep.* **2016**, *6*, 38603. [[CrossRef](#)]
11. Balamurugan, M.; Yun, G.; Ahn, K.S.; Kang, S.H. Revealing the beneficial effects of FeVO₄ nanoshell layer on the BiVO₄ inverse opal core layer for photoelectrochemical water oxidation. *J. Phys. Chem. C* **2017**, *121*, 7625–7634. [[CrossRef](#)]

12. Marberger, A.; Elsener, M.; Ferri, D.; Sagar, A.; Schermanz, K.; Krocher, O. Generation of NH₃ selective catalytic reduction active catalysts from decomposition of supported FeVO₄. *ACS Catal.* **2015**, *5*, 4180–4188. [CrossRef]
13. Yi, X.; Li, J.; Chen, Z.; Tok, A. Single-crystalline InVO₄ nanotubes by self-template-directed fabrication. *J. Am. Ceram. Soc.* **2010**, *93*, 596–600. [CrossRef]
14. Yu, Y.; Ju, P.; Zhang, D.; Han, X.; Yin, X.; Zheng, L.; Sun, C. Peroxidase-like activity of FeVO₄ nanobelts and its analytical application for optical detection of hydrogen peroxide. *Sens. Actuators B* **2016**, *233*, 162–172. [CrossRef]
15. López-Moreno, S.; Errandonea, D.; Pellicer-Porres, J.; Martínez-García, D.; Patwe, S.J.; Achary, S.N.; Tyagi, A.K.; Rodríguez-Hernández, P.; Muñoz, A.; Popescu, C. Stability of FeVO₄ under Pressure: An X-ray Diffraction and First-Principles Study. *Inorg. Chem.* **2018**, *57*, 7860–7876. [CrossRef]
16. Errandonea, D.; Gomis, O.; García-Domene, B.; Pellicer-Porres, J.; Katari, V.; Achary, S.N.; Tyagi, A.K.; Popescu, C. New polymorph of InVO₄: A high-pressure structure with six-coordinated vanadium. *Inorg. Chem.* **2013**, *52*, 12790–12798. [CrossRef] [PubMed]
17. Arisi, E.; Sánchez, S.; Leccabue, F.; Watts, B.; Bocelli, G.; Calderón, F.; Calestani, G.; Righi, L. Preparation and characterization of AlVO₄ compound. *J. Mater. Sci.* **2004**, *39*, 2107–2111. [CrossRef]
18. Muller, J.; Joubert, J. Synthèse sous haute pression d'oxygène d'une forme dense ordonnée de FeVO₄ et mise en évidence d'une variété allotropique de structure CrVO₄. *J. Solid State Chem.* **1975**, *14*, 8–13. [CrossRef]
19. Oka, Y.; Yao, T.; Yamamoto, N.; Ueda, Y.; Kawasaki, S.; Azuma, M.; Takano, M. Hydrothermal synthesis, crystal structure, and magnetic properties of FeVO₄-II. *J. Solid State Chem.* **1996**, *123*, 54–59. [CrossRef]
20. Gonzalez-Platas, J.; López-Moreno, S.; Bandiello, E.; Bettinelli, M.; Errandonea, D. Precise characterization of the rich structural landscape induced by pressure in multifunctional FeVO₄. *Inorg. Chem.* **2020**, *59*, 6623–6630. [CrossRef]
21. Young, A.; Schwartz, C. High pressure forms of CrVO₄ and FeVO₄. *Acta Crystallogr. Sect. A Found. Crystallogr.* **1962**, *15*, 1305–1305. [CrossRef]
22. Laves, F.; Young, A.P.; Schwartz, C.M. On the high-pressure form of FeVO₄. *Acta Cryst.* **1964**, *17*, 1476–1477. [CrossRef]
23. Ouahrani, T.; Garg, A.B.; Rao, R.; Rodríguez-Hernández, P.; Muñoz, A.; Badawi, M.; Errandonea, D. High-Pressure Properties of Wolframite-Type ScNbO₄. *J. Phys. Chem. C* **2022**, *126*, 4664–4676. [CrossRef]
24. Bader, R.F. Atoms in molecules. *Accounts Chem. Res.* **1985**, *18*, 9–15. [CrossRef]
25. Jones, R.O. Density functional theory: Its origins, rise to prominence, and future. *Rev. Mod. Phys.* **2015**, *87*, 897–923. [CrossRef]
26. Blöchl, P.E. Projector augmented-wave method. *Phys. Rev. B* **1994**, *50*, 17953–17979. [CrossRef] [PubMed]
27. Kresse, G.; Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **1999**, *59*, 1758–1775. [CrossRef]
28. Kresse, G.; Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **1993**, *47*, 558–561. [CrossRef]
29. Kresse, G.; Hafner, J. Ab initio molecular-dynamics simulation of the liquid-metal–amorphous-semiconductor transition in germanium. *Phys. Rev. B* **1994**, *49*, 14251–14269. [CrossRef]
30. Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54*, 11169–11186. [CrossRef]
31. Kresse, G.; Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **1996**, *6*, 15–50. [CrossRef]
32. Csonka, G.I.; Perdew, J.P.; Ruzsinszky, A.; Filippen, P.H.T.; Lebègue, S.; Paier, J.; Vydrov, O.A.; Ángyán, J.G. Assessing the performance of recent density functionals for bulk solids. *Phys. Rev. B* **2009**, *79*, 155107. [CrossRef]
33. Dudarev, S.L.; Botton, G.A.; Savrasov, S.Y.; Humphreys, C.J.; Sutton, A.P. Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+U study. *Phys. Rev. B* **1998**, *57*, 1505–1509. [CrossRef]
34. Ruiz-Fuertes, J.; Errandonea, D.; López-Moreno, S.; González, J.; Gomis, O.; Vilaplana, R.; Manjón, F.J.; Muñoz, A.; Rodríguez-Hernández, P.; Friedrich, A.; et al. High-pressure Raman spectroscopy and lattice-dynamics calculations on scintillating MgWO₄: Comparison with isomorphic compounds. *Phys. Rev. B* **2011**, *83*, 214112. [CrossRef]
35. López, S.; Romero, A.H.; Mejía-López, J.; Mazo-Zuluaga, J.; Restrepo, J. Structure and electronic properties of iron oxide clusters: A first-principles study. *Phys. Rev. B* **2009**, *80*, 085107. [CrossRef]
36. López-Moreno, S.; Romero, A.H.; Mejía-López, J.; Muñoz, A.; Roshchin, I.V. First-principles study of electronic, vibrational, elastic, and magnetic properties of FeF₂ as a function of pressure. *Phys. Rev. B* **2012**, *85*, 134110. <https://doi.org/10.1103/PhysRevB.85.134110>.
37. Mejía-López, J.; Mazo-Zuluaga, J.; López-Moreno, S.; Muñoz, F.; Duque, L.F.; Romero, A.H. Physical properties of quasi-one-dimensional MgO and Fe₃O₄-based nanostructures. *Phys. Rev. B* **2014**, *90*, 035411. [CrossRef]
38. Monkhorst, H.J.; Pack, J.D. Special points for Brillouin-zone integrations. *Phys. Rev. B* **1976**, *13*, 5188–5192. [CrossRef]
39. Parlinski, K. Computer Code PHONON. **2008**. Available online: <http://wolf.ifj.edu.pl/phonon> (accessed on 5 December 2022).
40. Romero-Vázquez, P.B.; López-Moreno, S.; Errandonea, D. First-principles study of AlCo₄ perovskites. *J. Phys. Chem. Solids* **2022**, *171*, 110979. [CrossRef]
41. Le Page, Y.; Saxe, P. Symmetry-general least-squares extraction of elastic data for strained materials from ab initio calculations of stress. *Phys. Rev. B* **2002**, *65*, 104104. [CrossRef]
42. Popelier, P.L.A. The QTAIM Perspective of Chemical Bonding. In *The Chemical Bond: Fundamental Aspects of Chemical Bonding*; John Wiley & Sons, Ltd: Hoboken, NJ, USA, 2014; chapter 8, pp. 271–308. [CrossRef]

43. Otero-de-la Roza, A.; Blanco, M.; Pendás, A.M.; Luaña, V. Critic: A new program for the topological analysis of solid-state electron densities. *Comput. Phys. Commun.* **2009**, *180*, 157–166. [[CrossRef](#)]
44. Otero-de-la Roza, A.; Johnson, E.R.; Luaña, V. Critic2: A program for real-space analysis of quantum chemical interactions in solids. *Comput. Phys. Commun.* **2014**, *185*, 1007–1018. [[CrossRef](#)]
45. Vega, D.; Almeida, D. AIM-UC: An application for QTAIM analysis. *J. Comput. Methods Sci. Eng.* **2014**, *14*, 131–136. [[CrossRef](#)]
46. Momma, K.; Izumi, F. VESTA3 for three-dimensional visualization of crystal, volumetric and morphology data. *J. Appl. Crystallog.* **2011**, *44*, 1272–1276. [[CrossRef](#)]
47. Birch, F. Finite elastic strain of cubic crystals. *Phys. Rev.* **1947**, *71*, 809–824. [[CrossRef](#)]
48. Touboul, M.; Ingrain, D. Syntheses et propriétés thermiques de InVO_4 et TlVO_4 . *J. Less Common Met.* **1980**, *71*, 55–62. [[CrossRef](#)]
49. Hotta, Y.; Ueda, Y.; Nakayama, N.; Kosuge, K.; Kachi, S.; Shimada, M.; Koizumi, M. Pressure-products diagram of FeVO_4 system ($0 \leq x \leq 0.5$). *J. Solid State Chem.* **1984**, *55*, 314–319. [[CrossRef](#)]
50. Errandonea, D. High pressure crystal structures of orthovanadates and their properties. *J. Appl. Phys.* **2020**, *128*, 040903. [[CrossRef](#)]
51. Díaz-Anichtchenko, D.; Errandonea, D. Comparative Study of the Compressibility of $\text{M}_3\text{V}_2\text{O}_8$ (M = Cd, Zn, Mg, Ni) Orthovanadates. *Crystals* **2022**, *12*. [[CrossRef](#)]
52. Botella, P.; Errandonea, D.; Garg, A.; Rodríguez-Hernández, P.; Muñoz, A.; Achary, S.; Vomiero, A. High-pressure characterization of the optical and electronic properties of InVO_4 , InNbO_4 , and InTaO_4 . *SN Appl. Scien.* **2019**, *1*, 389. [[CrossRef](#)]
53. Monteseuro, V.; Ruiz-Fuertes, J.; Contreras-García, J.; Rodríguez-Hernández, P.; Muñoz, A.; Errandonea, D. High pressure theoretical and experimental analysis of the bandgap of BaMoO_4 , PbMoO_4 , and CdMoO_4 . *Appl. Phys. Lett.* **2019**, *115*, 012102. [[CrossRef](#)]
54. Romero-Vázquez, P.B.; López-Moreno, S. Ab initio study of RaWO_4 : Comparison with isoelectronic tungstates. *J. Solid State Chem.* **2023**, *317*, 123709. [[CrossRef](#)]
55. Nye, J.F.; et al. *Physical properties of crystals: their representation by tensors and matrices*; Oxford university press, 1985.
56. Mouhat, F.; Coudert, F.X. Necessary and sufficient elastic stability conditions in various crystal systems. *Phys. Rev. B* **2014**, *90*, 224104. [[CrossRef](#)]
57. ping Feng, L.; tang Liu, Z.; jun Liu, Q. Structural, elastic and mechanical properties of orthorhombic SrHfO_3 under pressure from first-principles calculations. *Phys. B Condens. Matter* **2012**, *407*, 2009–2013. [[CrossRef](#)]
58. Najafvandezadeh, N.; López-Moreno, S.; Errandonea, D.; Pavone, P.; Draxl, C. First-principles study of elastic and thermal properties of scheelite-type molybdates and tungstates. *Mater. Today Commun.* **2020**, *24*, 101089. [[CrossRef](#)]
59. Voigt, W. *Lehrbuch Kristallphysik*; Springer: Berlin/Heidelberg, Germany, 1928. [[CrossRef](#)]
60. Reuss, A. Berechnung der Fließgrenze von Mischkristallen auf Grund der Plastizitätsbedingung für Einkristalle. *Angew Appl. Math. Mech.* **1929**, *9*, 49–58. [[CrossRef](#)]
61. Tian, Y.; Xu, B.; Zhao, Z. Microscopic theory of hardness and design of novel superhard crystals. *Int. J. Refract. Met. Hard. Mater.* **2012**, *33*, 93–106. [[CrossRef](#)]
62. Singh, J.; Sahoo, S.S.; Venkatakrisnan, K.; Vaitheeswaran, G.; Errandonea, D. High-pressure study of the aurophilic topological Dirac material AuI. *J. Alloys Compd.* **2022**, *928*, 167178. [[CrossRef](#)]
63. Prawoto, Y. Seeing auxetic materials from the mechanics point of view: A structural review on the negative Poisson's ratio. *Comput. Mater. Sci.* **2012**, *58*, 140–153. [[CrossRef](#)]
64. Liu, Y.; Jia, D.; Zhou, Y.; Zhou, Y.; Zhao, J.; Li, Q.; Liu, B. Discovery of ABO_4 scheelites with the extra low thermal conductivity through high-throughput calculations. *J. Mater.* **2020**, *6*, 702 – 711. [[CrossRef](#)]
65. Tvergaard, V.; Hutchinson, J.W. Microcracking in Ceramics Induced by Thermal Expansion or Elastic Anisotropy. *J. Am. Ceram. Soc.* **1988**, *71*, 157–166. [[CrossRef](#)]
66. Grimvall, G.; Magyari-Köpe, B.; Ozoliņš, V.; Persson, K.A. Lattice instabilities in metallic elements. *Rev. Mod. Phys.* **2012**, *84*, 945. [[CrossRef](#)]